

Secondary cells and batteries containing alkaline or other non-acid electrolytes — Secondary lithium cells and batteries for portable applications

The European Standard EN 61960:2004 has the status of a
British Standard

ICS 29.220.99

National foreword

This British Standard is the official English language version of EN 61960:2004. It is identical with IEC 61960:2003. Together with BS EN 61959:2004 and BS EN 62133:2003 it supersedes BS EN 61960-1:2001 and BS EN 61960-2:2002 which will be withdrawn on 1 March 2007.

The UK participation in its preparation was entrusted by Technical Committee PEL/21, Secondary cells and batteries, to Subcommittee PEL/21/1, Secondary cells and batteries containing alkaline and other non-acidic electrolytes, which has the responsibility to:

- aid enquirers to understand the text;
- present to the responsible international/European committee any enquiries on the interpretation, or proposals for change, and keep UK interests informed;
- monitor related international and European developments and promulgate them in the UK.

A list of organizations represented on this subcommittee can be obtained on request to its secretary.

Cross-references

The British Standards which implement international or European publications referred to in this document may be found in the *BSI Catalogue* under the section entitled “International Standards Correspondence Index”, or by using the “Search” facility of the *BSI Electronic Catalogue* or of British Standards Online.

This publication does not purport to include all the necessary provisions of a contract. Users are responsible for its correct application.

Compliance with a British Standard does not of itself confer immunity from legal obligations.

Summary of pages

This document comprises a front cover, an inside front cover, the EN title page, pages 2 to 18, an inside back cover and a back cover.

The BSI copyright notice displayed in this document indicates when the document was last issued.

This British Standard was published under the authority of the Standards Policy and Strategy Committee on 31 October 2005

© BSI 31 October 2005

ISBN 0 580 46525 X

Amendments issued since publication

Amd. No.	Date	Comments

EUROPEAN STANDARD

EN 61960

NORME EUROPÉENNE

EUROPÄISCHE NORM

June 2004

ICS 29.220.99

Partially supersedes EN 61960-1:2001 & EN 61960-2:2001

English version

Secondary cells and batteries containing alkaline
or other non-acid electrolytes –
Secondary lithium cells and batteries for portable applications
(IEC 61960:2003)

Accumulateurs alcalins et autres
accumulateurs à électrolyte non acide –
Eléments et batteries d'accumulateurs
au lithium pour applications portables
(CEI 61960:2003)

Akkumulatoren und Batterien
mit alkalischem oder anderen
nichtsäurehaltigen Elektrolyten –
Lithium-Akkumulatoren und -batterien
für tragbare Geräte
(IEC 61960:2003)

This European Standard was approved by CENELEC on 2004-03-01. CENELEC members are bound to comply with the CEN/CENELEC Internal Regulations which stipulate the conditions for giving this European Standard the status of a national standard without any alteration.

Up-to-date lists and bibliographical references concerning such national standards may be obtained on application to the Central Secretariat or to any CENELEC member.

This European Standard exists in three official versions (English, French, German). A version in any other language made by translation under the responsibility of a CENELEC member into its own language and notified to the Central Secretariat has the same status as the official versions.

CENELEC members are the national electrotechnical committees of Austria, Belgium, Cyprus, Czech Republic, Denmark, Estonia, Finland, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Slovakia, Slovenia, Spain, Sweden, Switzerland and United Kingdom.

CENELEC

European Committee for Electrotechnical Standardization
Comité Européen de Normalisation Electrotechnique
Europäisches Komitee für Elektrotechnische Normung

Central Secretariat: rue de Stassart 35, B - 1050 Brussels

Foreword

The text of document 21A/391/FDIS, future edition 1 of IEC 61960, prepared by SC 21A, Secondary cells and batteries containing alkaline or other non-acid electrolytes, of IEC TC 21, Secondary cells and batteries, was submitted to the IEC-CENELEC parallel vote and was approved by CENELEC as EN 61960 on 2004-03-01.

This European Standard, together with EN 61959:2004 and EN 62133:2003, supersedes EN 61960-1:2001 and EN 61960-2:2001.

The following dates were fixed:

- | | | |
|--|-------|------------|
| – latest date by which the EN has to be implemented at national level by publication of an identical national standard or by endorsement | (dop) | 2004-12-01 |
| – latest date by which the national standards conflicting with the EN have to be withdrawn | (dow) | 2007-03-01 |

Annex ZA has been added by CENELEC.

Endorsement notice

The text of the International Standard IEC 61960:2003 was approved by CENELEC as a European Standard without any modification.

In the official version, for Bibliography, the following notes have to be added for the standards indicated:

IEC 61434	NOTE Harmonized as EN 61434:1996 (not modified).
IEC 61959	NOTE Harmonized as EN 61959:2004 (not modified).
IEC 62133	NOTE Harmonized as EN 62133:2003 (not modified).

CONTENTS

1	Scope	5
2	Normative references	5
3	Terms and definitions	6
4	Parameter measurement tolerances	7
5	Designation and marking	7
5.1	Cell and battery designation	7
5.2	Cell or battery termination	8
5.3	Marking	8
6	Standard cells	9
7	Electrical tests.....	9
7.1	Charging procedure for test purposes	9
7.2	Discharge performance	9
7.2.1	Discharge performance at 20 °C (rated capacity).....	9
7.2.2	Discharge performance at –20 °C.....	10
7.2.3	High rate discharge performance at 20 °C	10
7.3	Charge (capacity) retention and recovery.....	10
7.4	Charge (capacity) recovery after long term storage	11
7.5	Endurance in cycles	11
7.6	Battery internal resistance	12
7.6.1	Measurement of the internal a.c. resistance	12
7.6.2	Measurement of the internal d.c. resistance	13
7.7	Electrostatic discharge (ESD)	13
7.7.1	Test procedure	13
7.7.2	Acceptance criterion	13
8	Test protocol and conditions for type approval	13
8.1	Test protocol	13
8.2	Conditions for type approval	14
8.2.1	Dimensions.....	14
8.2.2	Electrical tests	14
8.2.3	Conditional type approval.....	14
	Bibliography	17
	Annex ZA (normative) Normative references to international publications with their corresponding European publications	18

SECONDARY CELLS AND BATTERIES CONTAINING ALKALINE OR OTHER NON-ACID ELECTROLYTES – SECONDARY LITHIUM CELLS AND BATTERIES FOR PORTABLE APPLICATIONS

1 Scope

This International Standard specifies performance tests, designations, markings, dimensions and other requirements for secondary lithium single cells and batteries for portable applications.

The objective of this standard is to provide the purchasers and users of secondary lithium cells and batteries with a set of criteria with which they can judge the performance of secondary lithium cells and batteries offered by various manufacturers.

This standard defines a minimum required level of performance and a standardized methodology by which testing is performed and the results of this testing reported to the user. Hence, users will be able to establish the viability of commercially available cells and batteries via the declared specification and thus be able to select the cell or battery best suited for their intended application.

This standard covers secondary lithium cells and batteries with a range of chemistries. Each electrochemical couple has a characteristic voltage range over which it releases its electrical capacity, a characteristic nominal voltage and a characteristic end-of-discharge voltage during discharge. Users of secondary lithium cells and batteries are requested to consult the manufacturer for advice.

2 Normative references

The following referenced documents are indispensable for the application of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

IEC 60050-486, *International Electrotechnical Vocabulary (IEV) – Chapter 486: Secondary cells and batteries*

IEC 60051 (all parts), *Direct acting indicating analogue electrical measuring instruments and their accessories*

IEC 60485, *Digital electronic d.c. voltmeters and d.c. electronic analogue-to-digital converters*

IEC 61000-4-2, *Electromagnetic compatibility (EMC) – Part 4: Testing and measurement techniques – Section 2: Electrostatic discharge immunity test*

3 Terms and definitions

For the purpose of this International Standard, the definitions contained in IEC 60050-486 and the following apply.

3.1

charge (capacity) recovery

capacity that a cell or battery can deliver after the charge following the charge retention test according to 3.2

3.2

charge (capacity) retention

capacity that a cell or battery can deliver after storage, at a specific temperature, for a specific time without subsequent recharging as a percentage of the rated capacity

3.3

final voltage

end-of-discharge voltage

specified closed circuit voltage at which a discharge of a cell or battery is terminated

3.4

nominal voltage:

suitable approximate value of voltage used to identify the voltage of a cell or battery

NOTE 1 The nominal voltages of secondary lithium cells are given in Table 1.

NOTE 2 The nominal voltage of a battery of n series connected cells is equal to n times the nominal voltage of a single cell.

3.5

rated capacity

quantity of electricity C_5 Ah (ampere-hours) declared by the manufacturer which a single cell or battery can deliver during a 5-h period, when charged, stored and discharged under the conditions specified in 7.2.1

3.6

secondary lithium battery

unit which incorporates one or more secondary lithium cells and which is ready for use. It incorporates adequate housing and a terminal arrangement and may have electronic control devices

3.7

secondary lithium cell

secondary single cell whose electrical energy is derived from the oxidation and the reduction of lithium. It is not ready for use in an application because it is not yet fitted with its final housing, terminal arrangement and electronic control device

4 Parameter measurement tolerances

The overall accuracy of controlled or measured values, relative to the specified or actual values, shall be within these tolerances:

- a) $\pm 1 \%$ for voltage;
- b) $\pm 1 \%$ for current;
- c) $\pm 1 \%$ for capacity;
- d) $\pm 2 \text{ }^{\circ}\text{C}$ for temperature;
- e) $\pm 0,1 \%$ for time;
- f) $\pm 0,1 \%$ for mass;
- g) $\pm 0,1 \%$ for dimensions.

These tolerances comprise the combined accuracy of the measuring instruments, the measurement techniques used, and all other sources of error in the test procedure.

For assistance in selecting instrumentation, see IEC 60051 for analogue instruments and IEC 60485 for digital instruments. The details of the instrumentation used shall be provided in any report of results.

5 Designation and marking

5.1 Cell and battery designation

Batteries shall be designated with following form:

$$N_1 A_1 A_2 A_3 N_2 / N_3 / N_4 - N_5$$

Cells shall be designated with following form:

$$A_1 A_2 A_3 N_2 / N_3 / N_4$$

where

N_1 is the number of series connected cells in the battery;

A_1 designates the negative electrode system in which

L is lithium ion;

L is lithium metal or lithium alloy;

A_2 designates the positive electrode basis in which

C is cobalt;

N is nickel;

M is manganese;

V is vanadium;

T is titanium;

A_3 designates the shape of the cell in which

R is cylindrical;

P is prismatic;

N_2 is the maximum diameter (if R) or the maximum thickness (if P) in mm rounded up to the next whole number;

N_3 is the maximum width (if P) in mm rounded up to the next whole number (N_3 not shown if R);

N_4 is the maximum overall height in mm rounded up to the next whole number;

NOTE If any dimension is less than 1 mm, the units used are tenths of millimetres and the single number is written tN.

N_5 is the number of parallel connected cells if 2 or greater (not shown if value is 1).

- Examples:

ICR19/66 would designate a cylindrical Li-ion secondary cell, with a cobalt-based positive electrode, a maximum diameter between 18 mm and 19 mm, and an overall height between 65 mm and 66 mm.

ICP9/35/150 would designate a prismatic Li-ion secondary lithium cell, with a cobalt-based positive electrode, a maximum thickness between 8 mm and 9 mm, a maximum width between 34 mm and 35 mm, and an overall height between 149 mm and 150 mm.

ICPt9/35/48 would designate a prismatic Li-ion secondary lithium cell, with a cobalt-based positive electrode, a maximum thickness between 0,8 mm and 0,9 mm, a maximum width between 34 mm and 35 mm, and an overall height between 47 mm and 48 mm.

1ICR20/70 would designate a cylindrical Li-ion secondary battery with one single cell, a cobalt-based positive electrode, a diameter between 19 mm and 20 mm, and an overall height between 69 mm and 70 mm.

2ICP20/34/70 would designate a prismatic Li-ion secondary battery with two series connected cells, a cobalt-based positive electrode, a thickness between 19 and 20 mm, a width between 33 mm and 34 mm, and an overall height between 69 mm and 70 mm.

1ICP20/68/70-2 would designate a prismatic Li-ion secondary battery with two parallel connected cells, a cobalt-based positive electrode, a thickness between 19 mm and 20 mm, a width between 67 mm and 68 mm, and an overall height between 69 mm and 70 mm.

5.2 Cell or battery termination

This standard does not specify cell or battery termination.

5.3 Marking

Each cell or battery shall carry clear and durable markings giving the following information:

- rechargeable Li or Li-ion;
- battery or cell designation as specified in 5.1;
- polarity;
- date of manufacture (which may be in code);
- name or identification of manufacturer or supplier.

Battery markings shall provide the following additional information:

- rated capacity;
- nominal voltage.

6 Standard cells

Table 1 lists the secondary lithium cell(s) that are suitable for standardization and used in assembling batteries.

Table 1 – Standard secondary lithium cells

	1	2	3
Secondary lithium cell	ICR19/66	ICP9/35/48	ICR18/68
Height (mm)	64,0/65,2	47,2/48,0	65,9/67,2
Diameter (mm)	17,8/18,5	NA	16,2/17,1
Width (mm)	NA	33,4/34,2	NA
Thickness (mm)	NA	7,6/8,8	NA
Nominal voltage (V)	3,6	3,6	3,6
End-of-discharge voltage (V)	2,50	2,50	2,50
End-of-discharge voltage(V) for endurance (cycle life)	2,75	2,75	2,75

NOTE The end-of-discharge voltage of a battery of n series connected cells is equal to n times the end-of-discharge voltage of a single cell as given in Table 1 above.

7 Electrical tests

Unless otherwise stated, all tests that are described in this clause shall be performed in still air. Charge and discharge currents for the tests shall be based on the value of the rated capacity (C_5 Ah). These currents are expressed as a multiple of I_t A, where: I_t A = C_n Ah/1 h.

The minimum values required for each electrical test are stated in Table 3. Sample sizes and sequence of tests are described in Table 2.

7.1 Charging procedure for test purposes

Prior to charging, the cell or battery shall be discharged at $20\text{ °C} \pm 5\text{ °C}$ at a constant current of $0,2 I_t$ A, down to a specified end-of-discharge voltage.

Unless otherwise stated in this standard, cells or batteries shall be charged, in an ambient temperature of $20\text{ °C} \pm 5\text{ °C}$, using the method declared by the manufacturer.

7.2 Discharge performance

7.2.1 Discharge performance at 20 °C (rated capacity)

This test verifies the rated capacity of a cell or battery.

Step 1 – The cell or battery shall be charged in accordance with 7.1.

Step 2 – The cell or battery shall be stored, in an ambient temperature of $20\text{ °C} \pm 5\text{ °C}$, for not less than 1 h and not more than 4 h.

Step 3 – The cell or battery shall be discharged, in an ambient temperature of $20\text{ °C} \pm 5\text{ °C}$, at a constant current of $0,2\ I_t\text{ A}$, until its voltage is equal to the specified end-of-discharge voltage.

Step 4 – The capacity (Ah) delivered during step 3 shall be not less than 100 % of the rated capacity declared by the manufacturer. Steps 1 to 4 may be repeated up to four additional times, as necessary to satisfy this requirement.

7.2.2 Discharge performance at -20 °C

This test determines the capacity of the cell or battery at a low temperature.

Step 1 – The cell or battery shall be charged in accordance with 7.1.

Step 2 – The cell or battery shall be stored, in an ambient temperature of $-20\text{ °C} \pm 2\text{ °C}$, for not less than 16 h and not more than 24 h.

Step 3 – The cell or battery shall be discharged, in an ambient temperature of $-20\text{ °C} \pm 2\text{ °C}$, at a constant current of $0,2\ I_t\text{ A}$, until its voltage is equal to the specified end-of-discharge voltage.

Step 4 – The capacity (Ah), delivered during step 3, shall be not less than that specified for this characteristic in Table 3.

7.2.3 High rate discharge performance at 20 °C

This test determines the capacity of a cell or battery when discharged at a high rate. This test is not required if the cell or battery is not designed to be used at this rate.

Step 1 – The cell or battery shall be charged in accordance with 7.1.

Step 2 – The cell or battery shall be stored, in an ambient temperature of $20\text{ °C} \pm 5\text{ °C}$, for not less than 1 h and not more than 4 h.

Step 3 – The cell or battery shall be discharged, in an ambient temperature of $20\text{ °C} \pm 5\text{ °C}$, at a constant current of $1,0\ I_t\text{ A}$, until its voltage is equal to the specified end-of-discharge voltage.

Step 4 – The capacity (Ah) delivered during step 3 shall be not less than that specified for this characteristic in Table 3.

7.3 Charge (capacity) retention and recovery

This test determines firstly the capacity which a cell or battery retains after storage for an extended period of time, and secondly the capacity that can be recovered by a subsequent recharge.

Step 1 – The cell or battery shall be charged in accordance with 7.1.

Step 2 – The cell or battery shall be stored in an ambient temperature of $20\text{ °C} \pm 5\text{ °C}$, for 28 days.

Step 3 – The cell or battery shall be discharged, in an ambient temperature of $20\text{ °C} \pm 5\text{ °C}$, at a constant current of $0,2\ I_t\text{ A}$, until its voltage is equal to the specified end-of-discharge voltage.

Step 4 – The 28-day retained capacity (Ah) delivered, during step 3, shall be not less than that specified for this characteristic in Table 3.

Step 5 – The cell or battery shall then be charged in accordance with 7.1, within 24 h following the discharge of step 3.

Step 6 – The cell or battery shall be stored, in an ambient temperature of $20\text{ }^{\circ}\text{C} \pm 5\text{ }^{\circ}\text{C}$, for not less than 1 h and not more than 4 h.

Step 7 – The cell or battery shall be discharged, in an ambient temperature of $20\text{ }^{\circ}\text{C} \pm 5\text{ }^{\circ}\text{C}$, at a constant current of $0,2\text{ }I_t\text{ A}$, until its voltage is equal to the specified end-of-discharge voltage.

Step 8 – The recovery capacity (Ah) delivered, during step 6, shall be not less than that specified for this characteristic in Table 3.

7.4 Charge (capacity) recovery after long term storage

This test determines the capacity of a cell or battery after extended storage at 50 % state of charge, followed by a subsequent charge.

Step 1 – The cell or battery shall be charged in accordance with 7.1.

Step 2 – The cell or battery shall be discharged, in an ambient temperature of $20\text{ }^{\circ}\text{C} \pm 5\text{ }^{\circ}\text{C}$, at a constant current of $0,2\text{ }I_t\text{ A}$, for 2,5 h.

Step 3 – The cell or battery shall be stored in an ambient temperature of $40\text{ }^{\circ}\text{C} \pm 2\text{ }^{\circ}\text{C}$, for 90 days.

Step 4 – The cell or battery shall be charged, in an ambient temperature of $20\text{ }^{\circ}\text{C} \pm 5\text{ }^{\circ}\text{C}$, using the method declared by the manufacturer.

Step 5 – The cell or battery shall be stored, in an ambient temperature of $20\text{ }^{\circ}\text{C} \pm 5\text{ }^{\circ}\text{C}$, for not less than 1 h and not more than 4 h.

Step 6 – The cell or battery shall be discharged, in an ambient temperature of $20\text{ }^{\circ}\text{C} \pm 5\text{ }^{\circ}\text{C}$, at a constant current of $0,2\text{ }I_t\text{ A}$, until its voltage is equal to the specified end-of-discharge voltage.

Step 7 – The capacity (Ah) delivered during step 5 shall be not less than that specified for this characteristic in Table 3. Steps 4 and 5 may be repeated up to four additional times, as necessary to satisfy this requirement.

7.5 Endurance in cycles

This test determines the number of charge/discharge cycles which a cell or battery can endure before its useful capacity has been significantly depleted.

Step 1 – The cell or battery shall be charged in accordance with 7.1.

Step 2 – The cell or battery shall be discharged, in an ambient temperature of $20\text{ }^{\circ}\text{C} \pm 5\text{ }^{\circ}\text{C}$, at a constant current of $0,2\text{ }I_t\text{ A}$, until its voltage is equal to the specified end-of-discharge voltage.

Step 3 – The cell or battery shall be charged using the method declared by the manufacturer, in an ambient temperature of $20\text{ }^{\circ}\text{C} \pm 5\text{ }^{\circ}\text{C}$. For scheduling convenience the cell or battery may be stored between steps 2 and 3, and after step 3 for up to 1 h each.

Step 4 – The cell or battery shall be continuously discharged and charged as per steps 2 and 3 until its delivered capacity is less than 60 % of the rated capacity.

Step 5 – The number of times steps 2 and 3 are repeated (i.e. the cycle number) before being terminated by the criteria in step 4, shall be not less than that specified for this characteristic in Table 3.

7.6 Battery internal resistance

This test determines the internal resistance of a secondary lithium battery by either the alternating current (a.c.) or by the direct current (d.c.) method.

Should the need arise for the internal resistance to be measured by both a.c. and d.c. methods on the same battery, then the a.c. method shall be used first followed by the d.c. method. It is not necessary to discharge and charge the battery between conducting a.c. and d.c. measurements.

Step 1 – The battery shall be charged in accordance with 7.1.

Step 2 – The battery shall be stored, in an ambient temperature of $20\text{ }^{\circ}\text{C} \pm 5\text{ }^{\circ}\text{C}$, for not less than 1 h and not more than 4 h.

Step 3 – The measurement of internal resistance shall be performed in accordance with 7.6.1 or 7.6.2 in an ambient temperature of $20\text{ }^{\circ}\text{C} \pm 5\text{ }^{\circ}\text{C}$.

7.6.1 Measurement of the internal a.c. resistance

The alternating r.m.s. voltage, U_a , shall be measured while applying an alternating r.m.s. current, I_a , at the frequency of $1,0\text{ kHz} \pm 0,1\text{ kHz}$, to the battery, for a period of 1 s to 5 s.

All voltage measurements shall be made at the terminals of the battery independently of the contacts used to carry current.

The internal a.c. resistance, R_{ac} , is given by:

$$R_{ac} = \frac{U_a}{I_a} \text{ } (\Omega)$$

where

U_a is the alternating r.m.s. voltage;

I_a is the alternating r.m.s. current.

NOTE 1 The alternating current should be selected such that the peak voltage is less than 20 mV.

NOTE 2 This method will in fact measure the impedance, which at the frequency specified, is approximately equal to the resistance.

➤ Acceptance criterion

The internal a.c. resistance of the battery shall be not greater than the value of R_{ac} , declared by the manufacturer.

7.6.2 Measurement of the internal d.c. resistance

The battery shall be discharged at a constant current of $I_1 = 0,2 I_t$ A. At the end of a discharge period of 10 s, the discharge voltage U_1 under load shall be measured and recorded. The discharge current shall then be immediately increased to a value of $I_2 = 1,0 I_t$ A and the corresponding discharge voltage U_2 measured under load and recorded again at the end of a discharge period of 1 s.

All voltage measurements shall be made at the terminals of the battery independently of the contacts used to carry current.

The internal d.c. resistance R_{dc} of the battery shall be calculated using the following formula:

$$R_{dc} = \frac{U_1 - U_2}{I_2 - I_1} \text{ (}\Omega\text{)}$$

where

I_1, I_2 are the constant discharge currents;

U_1, U_2 are the appropriate voltages measured under load.

➤ Acceptance criterion

The internal d.c. resistance of the battery shall be not greater than the value of R_{dc} declared by the manufacturer.

7.7 Electrostatic discharge (ESD)

This test is to evaluate the ability of a battery to withstand electrostatic discharge.

This test shall be conducted on a battery containing electronic protection devices, such as diodes, transistors or integrated circuits.

7.7.1 Test procedure

This test shall be carried out in accordance with IEC 61000-4-2, which concerns electronic discharge requirements (see Clauses 1 to 8).

The batteries shall be tested for contact discharge at 4 kV and air discharge at 8 kV.

7.7.2 Acceptance criterion

The battery shall operate with all protection circuits operational.

8 Test protocol and conditions for type approval

8.1 Test protocol

The sample size and protocol for conducting the electrical tests in Clause 7 are given in Table 2.

8.2 Conditions for type approval

8.2.1 Dimensions

The dimensions of the cell or battery shall not exceed the manufacturers' specified values and those values listed in Table 1.

8.2.2 Electrical tests

8.2.2.1 The manufacturer shall declare the rated capacity (C_5 Ah) of the cell or battery based on its performance under the conditions specified in 7.2.1 and in Table 3.

8.2.2.2 In order to meet the requirements of this standard, all samples shall meet all the performances specified in Table 3. The minimum levels for meeting the requirements of the electrical tests are expressed as percentages of the rated capacity.

8.2.2.3 If the test results do not meet the conditions of 8.2.2.2, the test can be repeated with new samples, provided that, on any test, not more than one sample failed to reach the performance specified in Table 3.

8.2.2.4 As an alternative to repeating the tests, a manufacturer may reduce the declared rated capacity of the battery to a value such that all test results do meet the conditions of 8.2.2.2.

8.2.3 Conditional type approval

The cell or battery can be considered conditionally type approved prior to the completion of the charge (capacity) recovery after storage test specified in 7.4 and the endurance in cycles test specified in 7.5 if:

- a) 20 % of the required cycles of the endurance test have been completed and the capacity delivered during step 2 remains above 85 % of the rated capacity, and
- b) the requirements of all the other tests specified in Clause 7 have been met.

Table 2 – Sample sizes and sequence of tests

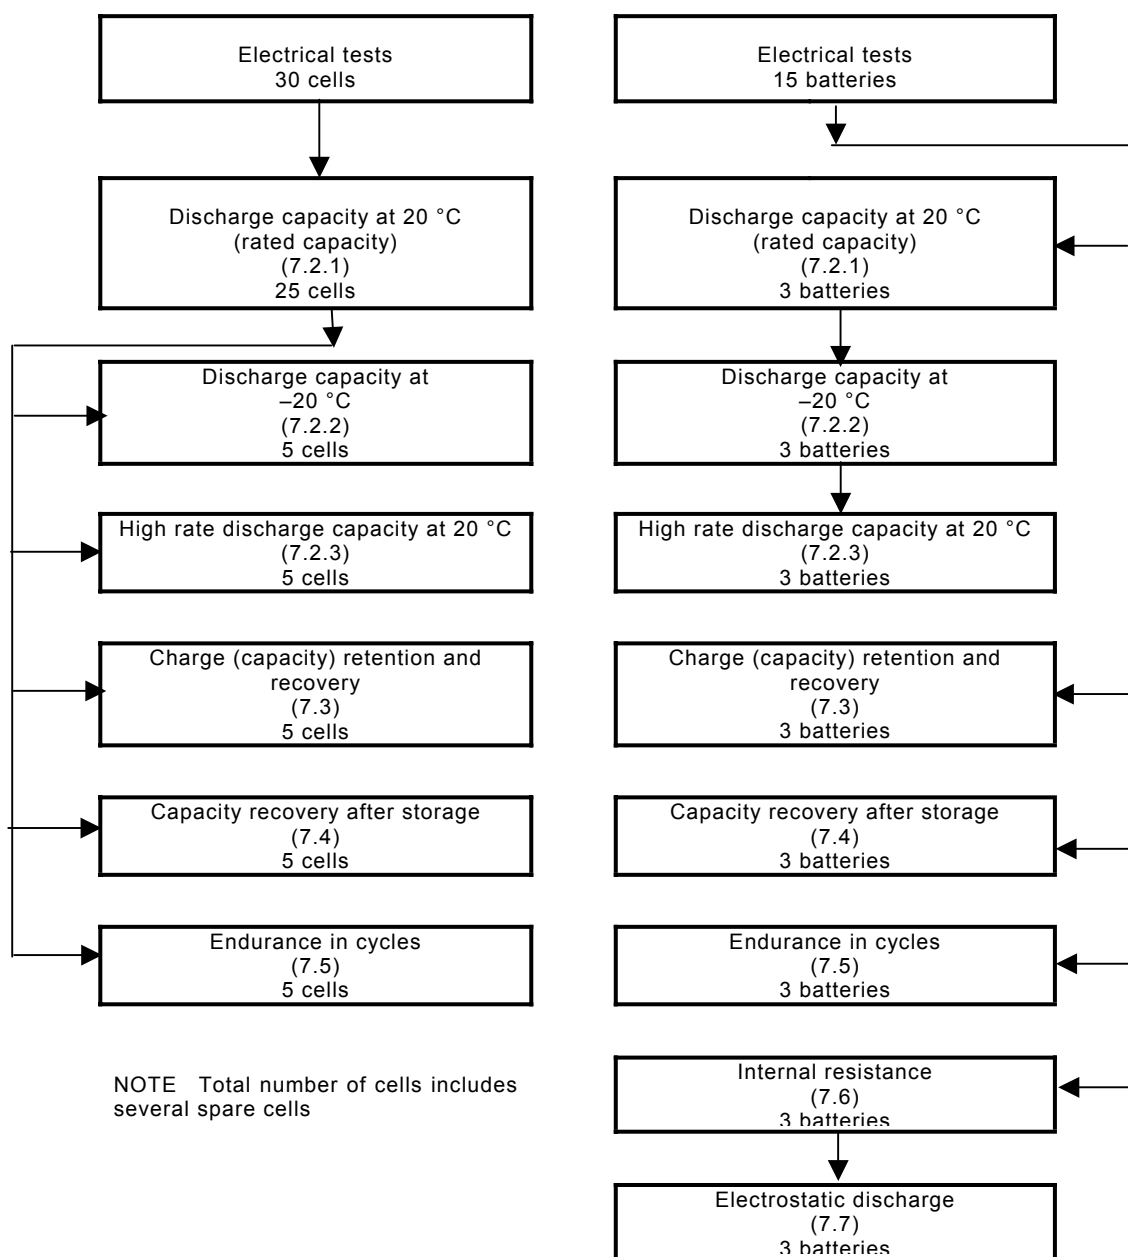


Table 3 – Minimum requirements for each type of standard secondary lithium cells and batteries

Parameter	Reference subclause	Acceptance criteria – cells	Acceptance criteria – batteries
Capacity at 20 °C ± 5 °C (rated capacity)	7.2.1	100 % C ₅ Ah	100 % C ₅ Ah
Capacity at –20 °C ± 2 °C	7.2.2	30 % C ₅ Ah	30 % C ₅ Ah
High rate discharge capacity at 20 °C ± 5 °C	7.2.3	70 % C ₅ Ah	60 % C ₅ Ah
Charge (capacity) retention	7.3	70 % C ₅ Ah	60 % C ₅ Ah
Charge (capacity) recovery	7.3	85 % C ₅ Ah	85 % C ₅ Ah
Capacity recovery after storage	7.4	50 % C ₅ Ah	50 % C ₅ Ah
Endurance in cycles	7.5	400 cycles	300 cycles
Electrostatic discharge	7.7	n.a.	Operational

Bibliography

IEC 61434, *Secondary cells and batteries containing alkaline or other non-acid electrolytes – Guide to the designation of current in alkaline secondary cell and battery standards*

IEC 61959, *Secondary cells and batteries containing alkaline or other non-acid electrolytes – Mechanical tests for sealed portable secondary cells and batteries*

IEC 62133, *Secondary cells and batteries containing alkaline or other non-acid electrolytes – Safety requirements for portable sealed secondary cells, and for batteries made from them, for use in portable applications*

Annex ZA (normative)

Normative references to international publications with their corresponding European publications

The following referenced documents are indispensable for the application of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

NOTE Where an international publication has been modified by common modifications, indicated by (mod), the relevant EN/HD applies.

<u>Publication</u>	<u>Year</u>	<u>Title</u>	<u>EN/HD</u>	<u>Year</u>
IEC 60050-486	– ¹⁾	International Electrotechnical Vocabulary (IEV) Chapter 486: Secondary cells and batteries	–	–
IEC 60051-1	Series	Direct acting indicating analogue electrical measuring instruments and their accessories Part 1: Definitions and general requirements common to all parts	EN 60051-1	Series
IEC 60485	– ¹⁾	Digital electronic d.c. voltmeters and d.c. electronic analogue-to-digital converters	–	–
IEC 61000-4-2	– ¹⁾	Electromagnetic compatibility (EMC) Part 4-2: Testing and measurement techniques - Electrostatic discharge immunity test	EN 61000-4-2	1995 ²⁾

¹⁾ undated reference.

²⁾ valid edition at date of issue.

BSI — British Standards Institution

BSI is the independent national body responsible for preparing British Standards. It presents the UK view on standards in Europe and at the international level. It is incorporated by Royal Charter.

Revisions

British Standards are updated by amendment or revision. Users of British Standards should make sure that they possess the latest amendments or editions.

It is the constant aim of BSI to improve the quality of our products and services. We would be grateful if anyone finding an inaccuracy or ambiguity while using this British Standard would inform the Secretary of the technical committee responsible, the identity of which can be found on the inside front cover.
Tel: +44 (0)20 8996 9000. Fax: +44 (0)20 8996 7400.

BSI offers members an individual updating service called PLUS which ensures that subscribers automatically receive the latest editions of standards.

Buying standards

Orders for all BSI, international and foreign standards publications should be addressed to Customer Services. Tel: +44 (0)20 8996 9001.
Fax: +44 (0)20 8996 7001. Email: orders@bsi-global.com. Standards are also available from the BSI website at <http://www.bsi-global.com>.

In response to orders for international standards, it is BSI policy to supply the BSI implementation of those that have been published as British Standards, unless otherwise requested.

Information on standards

BSI provides a wide range of information on national, European and international standards through its Library and its Technical Help to Exporters Service. Various BSI electronic information services are also available which give details on all its products and services. Contact the Information Centre.
Tel: +44 (0)20 8996 7111. Fax: +44 (0)20 8996 7048. Email: info@bsi-global.com.

Subscribing members of BSI are kept up to date with standards developments and receive substantial discounts on the purchase price of standards. For details of these and other benefits contact Membership Administration.
Tel: +44 (0)20 8996 7002. Fax: +44 (0)20 8996 7001.
Email: membership@bsi-global.com.

Information regarding online access to British Standards via British Standards Online can be found at <http://www.bsi-global.com/bsonline>.

Further information about BSI is available on the BSI website at <http://www.bsi-global.com>.

Copyright

Copyright subsists in all BSI publications. BSI also holds the copyright, in the UK, of the publications of the international standardization bodies. Except as permitted under the Copyright, Designs and Patents Act 1988 no extract may be reproduced, stored in a retrieval system or transmitted in any form or by any means – electronic, photocopying, recording or otherwise – without prior written permission from BSI.

This does not preclude the free use, in the course of implementing the standard, of necessary details such as symbols, and size, type or grade designations. If these details are to be used for any other purpose than implementation then the prior written permission of BSI must be obtained.

Details and advice can be obtained from the Copyright & Licensing Manager.
Tel: +44 (0)20 8996 7070. Fax: +44 (0)20 8996 7553.
Email: copyright@bsi-global.com.